



Material & Engineering Laboratory-Kaohsiung

# Test Report



Report No. : KB-14-12007XA  
C-14-23659  
Page No. : 1 OF 1  
Date of Report : Nov. 17, 2014

**Applicant** HO YU TECHNOLOGY CO., LTD.  
**Address** No.31.Ln,295.Sec 3,Hanxi W.Rd.Beitun Dist,Taichuan City 406,Taiwan(R.O.C)  
**Supplier** HO YU TECHNOLOGY CO., LTD.  
**Sample Name** VQ-800 Concrete nano sealer and hardener  
**Sample Submitted By** HO YU TECHNOLOGY CO., LTD.  
**Date of Testing** Sep. 10, 2014  
**Testing Method** Sep. 10, 2014~Nov. 17, 2014  
**Remark** The information mentioned in the above section is provided by Client  
 (Exclude Date of Sample Received and Date of Testing)

### Test Conditions :

Mortars of Mixing Rate(By Weight )= Cement (Type I) : Granded Standard Sand : Water  
= 500 : 1375 : 242

### Test Results :

| Test Items                | Test Method | Test Results   |                       |
|---------------------------|-------------|--|-----------------------|
|                           |             | Tensile strength (kgf/cm <sup>2</sup> )  | Refer. CNS 1011(1983) |
|                           |             | Test group (Surface coating agents)  | 33.6                  |
| Tensile strength Ratio(%) | -----       | $\frac{\text{Test group} - \text{Control group}}{\text{Control group}} \times 100\%$ | 31.3                  |

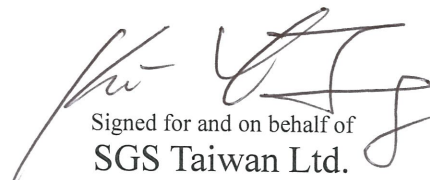
Note: 1: The specimen of test group after removing the molds stored at room temperature in air until age of 28 days. Operating procedure of VQ-800 performed by the customer about 2 hours. The test specimen stored at room temperature in air 9 days after VQ-800 operating procedure.

2.The curing procedure: control and Test Group are stored at room temperature.

3.This Test Report is an additional original report of KB-14-12007X. Issued date : Nov. 11, 2014.

----- oOo -----

The required specification(s) offered in this test report is/are for reference only.  
The conformity judgment is at the Applicant's final verdict.

  
Signed for and on behalf of  
SGS Taiwan Ltd.

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.